

Half-Periodic Josephson Effect in an s -Wave Superconductor - Normal Metal - d -Wave Superconductor Junction

Alexandre M. Zagoskin

Department of Physics and Astronomy, The University of British Columbia, 6224 Agricultural Rd., Vancouver, B.C., V6T 1Z1, Canada; Email zagoskin@physics.ubc.ca
(Preprint: cond-mat/9702123)

We predict that the Josephson current in a clean s -wave superconductor-normal metal- d -wave superconductor junction is periodic in superconducting phase difference φ with period π instead of 2π . The frequency of non-stationary Josephson effect is correspondingly $2\omega_J = 4eV$. The effect is due to coexistence in the normal layer of current carrying Andreev levels with phase differences φ and $\varphi + \pi$.

The Josephson effect in superconductor-normal metal-superconductor (SNS) junctions differs from the effect in tunneling junctions in several important aspects [1]. In particular, in a long clean SNS junction at $T = 0$ the Josephson current, $I_J(\varphi)$, is a sawtooth function of superconducting phase difference φ [2–4] (solid line in Fig.1a), in contrast to $I_c \sin \varphi$ dependence in tunneling junctions [1]. The reason of this behaviour is that the Josephson current is transferred through the normal layer by current carrying Andreev levels, formed due to subgap Andreev reflections of electrons and holes from the non-diagonal pairing potential of superconductors [4,5]. Positions of these levels, and therefore the current, depend on φ .

In this Letter we consider the case when one of the superconductors has d -wave pairing symmetry: s -wave superconductor - normal metal - d -wave superconductor ("SND") junction (Fig.2a). There is a strong evidence that such pairing is realized in superconducting cuprates, based particularly on phase sensitive measurements [6,7]. The experimental realization of SND junction is feasible, and could provide additional information about superconductivity in cuprates. Both tunneling and SNS junctions between conventional and d -wave superconductors are now being actively investigated [8].

We predict that SND junctions will combine properties of conventional and so called π -junction [9,10] with negative critical current [11](Fig.1a, dashed line). As a result, they exhibit *half-periodic Josephson effect*, with $I(\phi)$ being π -periodic function of phase (instead of 2π), which can be detected, e.g., by doubling of frequency of non-stationary Josephson effect.

The physical picture of the effect is as follows. In d -wave superconductors the order parameter can have either sign depending on the momentum direction on the Fermi surface, which can be treated as an additional, intrinsic phase π [12].

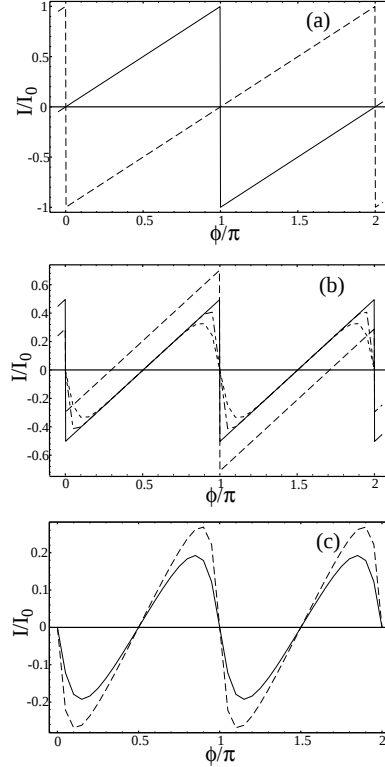


FIG. 1. (a) Current-phase characteristics of a clean SNS junction at zero temperature: conventional ("zero"-) junction (solid line); π -junction (dashed line). (b) Current-phase characteristics of half-periodic Josephson current: $Z = 0, T = 0$ (solid line); $Z = 2^{1/2} - 1, T = 0$ (dashed line); $Z = 0, L/l_T = 0.2$ (dash-dotted line); $Z = 0, L/l_T = 0.5$ (dotted line). Disbalance function Z is defined in Eq.(9). (c) Current-phase characteristics of half-periodic Josephson current at finite normal scattering: $Z = 0; L/l_i = 0.05$ (dashed line); 0.1 (solid line).

Therefore the Andreev levels in SND junction depend (instead of φ) on effective phase difference

$$\tilde{\varphi}(\mathbf{k}_{\parallel}) = \varphi + \pi \vartheta(-\Delta_{\hat{q}}), \quad (1)$$

where $\vartheta(x)$ is the Heaviside step function. Unit vector $\hat{q}$ gives the direction of the wave vector of transmitted state in d -wave superconductor, $\mathbf{q}$, with components $\mathbf{k}_{\parallel}$ (parallel to the interface) and $q_z(E)$ (Fig.2b). There are thus two sets of Andreev levels in the normal layer: with $\tilde{\varphi} = \varphi$ ($\Delta_{\hat{q}}$ positive) and $\tilde{\varphi} = \varphi + \pi$ ($\Delta_{\hat{q}}$ negative).

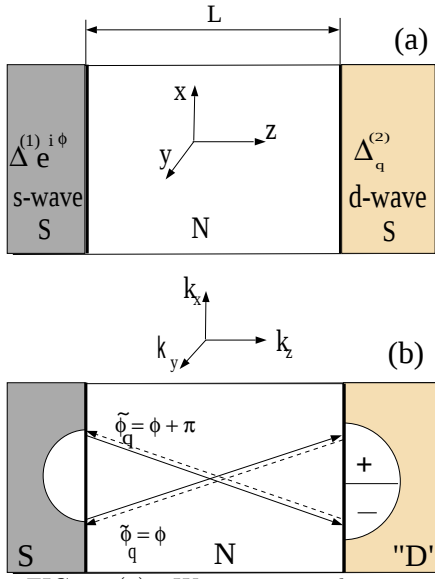


FIG. 2. (a) *s*-Wave superconductor - normal metal - *d*-wave superconductor junction ("SND"-junction). We can choose real order parameter in *d*-wave superconductor. (b) Zero- and π - Andreev levels in a clean SND junction.

The Josephson current through π -levels will be a 2π -periodic function of phase, shifted by π with respect to the current carried by zero levels. The resulting current is π -periodic in phase (Fig.1b).

From the Josephson relation $\partial_t \varphi = 2eV$ we see that the Josephson frequency doubles: $\tilde{\omega}_J = 2\omega_J = 4eV$.

In our further analysis we assume that the following conditions are satisfied:

$$\max(\xi_0) \ll L \ll l_T, l_\varepsilon, l_i. \quad (2)$$

where L is the width of the normal metal layer, $\max(\xi_0)$ the larger of the correlation length in either superconductor, l_i, l_ε are elastic and inelastic scattering length respectively, and $l_T = v_F / (2\pi k_B T)$ is the normal metal coherence length in the clean limit. The latter is the characteristic coupling length in SNS junction [2,3,5], and can be much larger than ξ_0 (especially in case of cuprates [13]). In silver, e.g., at $1K$ $l_T = 1.67 \cdot 10^{-4}$ cm, compared to $\xi_0 \sim 10^{-5}$ cm typical for conventional superconductors.

Andreev levels in the normal layer are obtained by solving Bogoliubov-de Gennes equations for the two-component wave function in both superconductors and normal layer, separately for each $\mathbf{k}_\parallel$ -mode, and matching the wave functions at the interfaces [14]; for the SND junction we have:

$$\begin{pmatrix} \mathcal{H} - \frac{k_F^2 - k_\parallel^2}{2m} & \Delta(z) \\ \Delta^*(z) & -\left(\mathcal{H} - \frac{k_F^2 - k_\parallel^2}{2m}\right) \end{pmatrix} \begin{pmatrix} u(z) \\ v(z) \end{pmatrix} = E \begin{pmatrix} u(z) \\ v(z) \end{pmatrix}. \quad (3)$$

Here $\mathcal{H} = -\frac{1}{2m} \nabla_z^2$ is the one-particle Hamiltonian; $\Delta(z)$ is the non-diagonal potential (which is zero in normal

layer, $\Delta^{(1)} e^{i\varphi}$ in *s*-wave superconductor, and $\Delta_q^{(2)}$ in *d*-wave superconductor; we choose real $\Delta^{(1)}, \Delta_q^{(2)}$). This standard approximation is justified by the condition $\xi_0 \ll L$ [14]. We assume for simplicity the same value of k_F in all three regions. The corrections due to differences in k_F and finite normal scattering on the interface will be considered elsewhere.

In the normal layer the normal component of the momentum of an electron (hole) with energy E and tangential momentum $\mathbf{k}_\parallel$ is $k_z^{e,h}(E) = \sqrt{k_F^2 - k_\parallel^2 \pm 2mE}$. In the superconductor, for a subgap quasiparticle, $E < |\Delta|$, it transforms into

$$q_z^\pm(E) = k_z(0) \sqrt{1 \pm i \frac{|\Delta|}{k_z(0)^2/2m} \sqrt{1 - \frac{E^2}{|\Delta|^2}}}. \quad (4)$$

If $|\Delta| \ll \frac{k_z^2(0)}{2m}$, then $\Re q_z^\pm \approx k_z(0)$, i.e. the quasiparticle momentum does not change direction in the superconductor: $\hat{q} \approx \hat{k}$, $\mathbf{k} = (\mathbf{k}_\parallel, k_z)$. Therefore the momentum of the quasiparticle in the normal layer determines the value $\Delta_{\hat{k}}$ of the *d*-wave order parameter entering Bogoliubov-de Gennes equations (3), and the effective phase difference for given Andreev level (Fig.2b).

Under the above conditions the energies of low-lying Andreev levels ($E \ll |\Delta|$) are given by

$$(k_z^e(E) - k_z^h(E)) L \pm \tilde{\varphi}^{(\mathbf{k}_\parallel)} = \pi(2n+1); n = 0, \pm 1, \pm 2, \dots \quad (5)$$

This is a direct generalization of the result by Kulik [5].

The Josephson current through the contact can be calculated using the low-energy excitation spectrum determined from (5) [4,15], to yield at $T = 0$:

$$I_J(\varphi) = \sum_{\vec{\kappa}} \frac{2ev_F^{(\vec{\kappa})}}{\pi L} \sum_{n=1}^{\infty} (-1)^{n+1} \frac{\sin n\tilde{\varphi}^{(\vec{\kappa})}}{n}. \quad (6)$$

Here $\tilde{\varphi}^{(\vec{\kappa})}$ is the effective phase shift, and $v_F^{(\vec{\kappa})}$ is the normal to the interface component of Fermi velocity in a mode with tangential momentum $\mathbf{k}_\parallel = \vec{\kappa}$: $(mv_F^{(\vec{\kappa})})^2 + \vec{\kappa}^2 = k_F^2$. The summation $\sum_{\vec{\kappa}} = S \int_{|\vec{\kappa}| \leq k_F} d\vec{\kappa}_x d\vec{\kappa}_y$ is extended over all allowed tangential modes [16]; S is the area of the junction.

It follows from (6) that the Josephson current in clean SND junction is indeed a sum of independent contributions of zero- and π -modes:

$$I_J(\varphi) = I_0 \left(\alpha^{(+)} F(\varphi) + \alpha^{(-)} F(\varphi + \pi) \right) = \quad (7)$$

$$= \frac{I_0}{2} (F(\varphi) + F(\varphi + \pi) + Z(F(\varphi) - F(\varphi + \pi))). \quad (8)$$

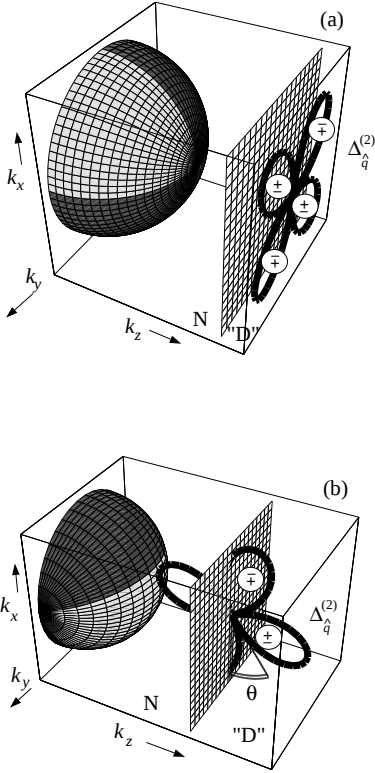


FIG. 3. On calculation of disbalance function at different orientations of d -wave superconductor with respect to the interface: white regions on the Fermi surface (in normal metal) correspond to zero modes, shadowed - to π -modes, or vice versa. (a) Interface parallel to $x^2 - y^2$ -plane. (b) Interface normal to $x^2 - y^2$ -plane; θ is the angle between the SN interface and the nodal direction in $x^2 - y^2$ -plane.

Here $F(x) = \frac{2}{\pi} \sum_{n=1}^{\infty} (-1)^{n+1} \frac{\sin nx}{n}$ is the 2π -periodic sawtooth of unit amplitude; $I_0 = \frac{e}{L} \sum_{\vec{k}} v_{Fz}^{(\vec{k})}$ is the critical current of clean SNS junction at zero temperature [3,4]; and weight factors $\alpha^{(\pm)} = \sum_{\vec{k}}^{\pm} v_{Fz}^{(\vec{k})} / \sum_{\vec{k}} v_{Fz}^{(\vec{k})}$, where the $\pm$ -summation is extended over zero- and π -modes respectively.

The ratio between the two contributions in (7) generally depends on the orientation of the d -superconductor with respect to the interface, parametrized by some angles θ_a , through the disbalance function,

$$Z(\theta_a) = \frac{\alpha^{(+)}(\theta_a) - \alpha^{(-)}(\theta_a)}{\alpha^{(+)}(\theta_a) + \alpha^{(-)}(\theta_a)}; \quad |Z(\theta_a)| \leq 1; \quad (9)$$

$Z = \pm 1$ corresponds to purely zero- or π - junction [9,10] respectively; $Z = 0$ when amplitudes of the contributions from zero- and π -levels are equal.

Due to nonsinusoidal form of the current-phase characteristics, the current is not zero if $Z(\theta_a) = 0$ (as it would be in case of tunneling contact [10], with $\sin \varphi$ in place of $F(\varphi)$ [17]). On the contrary, the resulting current is π -periodic in phase (Fig.1b), and its critical value is halved.

The simplest case is an SND junction where $x^2 - y^2$ -plane of the d -wave superconductor is parallel to the interface

(Fig.3a): then $Z(\theta_a) \equiv 0$ by symmetry. For cuprates, this (001)-plane is also the easiest cleavage plane, which makes it the best candidate for experimental observation of the effect.

Another possibility is to choose the interface normal to that plane. It is easy to see that in this case the disbalance function depends on a single angle θ between the SN interface and the nodal direction in $x^2 - y^2$ -plane (see Fig.3b), and $Z(\theta) = \pm (\sqrt{2} \cos[\theta - \frac{\pi}{4}] - 1)$; ($0 \leq \theta \leq \frac{\pi}{2}$). Since $|Z(\theta)| \leq (\sqrt{2} - 1)$, the Josephson current in this case always contains a π -periodic component (see Fig.1b).

It is worth noting that in case of "DND" junction between two d -wave superconductors the half-periodic Josephson effect is present as well, but it disappears at certain orientations of the crystals. If the junction interface is parallel to $x^2 - y^2$ -plane of both superconductors, then $Z(\alpha) = \pm (1 - 4 \frac{\alpha}{\pi})$. Here $0 \leq \alpha \leq \frac{\pi}{2}$ is the angle between nodal directions in the superconductors, and the effect is absent if $\alpha = 0$ or $\frac{\pi}{2}$.

So far we did not consider the effects of nonmagnetic impurity scattering and finite temperature.

At finite temperatures the condition $E \ll |\Delta^{(i)}|$ will be met for almost all of the Fermi surface if

$$k_B T \sim E \ll |\Delta^{(1)}|; \max |\Delta_{\vec{k}}^{(2)}|; \quad (10)$$

corrections to the current from the regions close to the nodal lines will be small by the same parameter, $k_B T / \max |\Delta_{\vec{k}}^{(2)}|$. This additional condition on temperature is in fact less restrictive than the one following from (2).

Weak scattering can be taken into account via broadening of Andreev levels due to finite elastic scattering time, $\tau = l_i / v_F$ [18]. Using the approach of [19], we find for $L/l_i, L/l_T \ll 1$:

$$I_J(\varphi) = \sum_{\vec{k}} \frac{2e v_{Fz}^{(\vec{k})}}{\pi L} \sum_{n=1}^{\infty} (-1)^{n+1} \exp \left[-2n \frac{L}{l_i^{(\vec{k})}} \right] \times \frac{(L/l_T^{(\vec{k})}) \sin n \tilde{\varphi}^{(\vec{k})}}{\sinh(nL/l_T^{(\vec{k})})} \quad (11)$$

(see Fig.1b,c). Here $l_i^{(\vec{k})} = l_i \frac{v_{Fz}^{(\vec{k})}}{v_F}$, $l_T^{(\vec{k})} = l_T \frac{v_{Fz}^{(\vec{k})}}{v_F}$ are effective scattering and coherence length in mode $\vec{k}$ respectively. The effect survives finite temperature and weak elastic scattering in the normal layer.

In the limit of strong elastic scattering, $L \gg l_i$, or at higher temperatures, $L \gg l_T$, the sawtooth current-phase dependence in long SNS junctions reduces to the sinusoidal one [18], and the effect disappears due to cancellation of contributions from zero- and π -modes.

Note added:

After this paper was submitted, the preprint [20] appeared, where analogous conclusions were made in the case of short SND junction ($L \ll \min(\xi_0)$).

ACKNOWLEDGMENTS

I would like to thank I. Affleck, D. Bonn, A. Dubin, D.L. Feder, I. Herbut, S. Kivelson, M. Oshikawa, and P.C.E. Stamp for fruitful discussions and criticism, and P.F. Bagwell and Y. Tanaka for kindly acquainting me with the results of their current research.

-
- [1] A. Barone and G. Paternò, *Physics and Applications of the Josephson Effect*, John Wiley & Sons, 1982.
 - [2] G. Ishii, Progr. Theor. Phys. **44**, 1525 (1970).
 - [3] A.V. Svidzinskii, T.N. Antsygina, and E.N. Bratus', Zh. Exp. Teor. Phys. **61**, 1612 (1971) (Sov. Phys.-JETP **34**, 860 (1972)).
 - [4] J. Bardeen and J.L. Johnson, Phys. Rev. B **5**, 72 (1972).
 - [5] I.O. Kulik, Zh. Exp. Teor. Phys. **57**, 1745 (1969) (Sov. Phys.-JETP **30** 944 (1970)).
 - [6] D.J. Van Harlingen, Rev. Mod. Phys. **67**, 515 (1995).
 - [7] C.C. Tsuei *et al.*, Science **271**, 329 (1996).
 - [8] Y. Tanaka, Phys. Rev. Lett. **72**, 3871 (1994); Y. Tanaka and S. Kashiwaya, Phys. Rev. B **53**, 11 957 (1996); preprint (1997); J.-X. Zhu, Z.D. Wang, and H.X. Tang, Phys. Rev. B **54**, 7354 (1996); T.P. Devereaux and P. Fulde, Phys. Rev. B **47**, 14 638 (1993).
 - [9] V.B. Geshkenbein, A.I. Larkin, and A. Barone, Phys. Rev. B **36**, 235 (1987).
 - [10] M. Sigrist and T.M. Rice, J. Phys. Soc. Japan **61**, 4283 (1992).
 - [11] A superconducting ring with an odd number of π -junctions contains a half-integer number of flux quanta, $\Phi = (n + 1/2) \frac{hc}{2e}$; this effect was observed in cuprates [7].
 - [12] M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
 - [13] K. Bedell *et al.*, Eds., *High Temperature Superconductivity*, Addison-Wesley (1989).
 - [14] See e.g. M. Hurd and G. Wendin, Phys. Rev. B **49**, 15258 (1994).
 - [15] B.J. van Wees, K.M.H. Lenssen, and C.J.P.M. Harmans, Phys. Rev. B **44**, 470 (1991).
 - [16] The corrections from "grazing" trajectories (with $k_{\parallel} \approx k_F$) are negligible by the parameter $|\Delta^{(1,2)}|/E_F \ll 1$.
 - [17] Tanaka [8] have shown that actually in this case the Josephson current is determined by the contribution of the next order in Δ , leading to $\sin 2\phi$ current-phase dependence.
 - [18] I.O. Kulik and Yu.N. Mitsai, Fiz. Nizk. Temp. **1**, 906 (1975) (Sov. J. Low Temp. Phys. **1**, 434 (1975)).
 - [19] A. Kadigrobov, A. Zagoskin, R.I. Shekhter, and M. Jonson, Phys. Rev. B **52**, R8662 (1995).
 - [20] R.A. Riedel and P.F. Bagwell, preprint (1997).